arXiv:0904.4022v2 [cond-mat.supr-con] 7 Apr 2010

The orbital characters of bands in iron-based superconductor $\mathbf{BaFe_{1.85}Co_{0.15}As_2}$

Y. Zhang[1], B. Zhou[1], F. Chen[1], J. Wei[1], M. Xu[1], L. X. Yang[1], C. Fang[2], W. F. Tsai[2], G. H. Cao[3], Z. A. Xu[3], M. Arita[4], H. Hayashi[4], J. Jiang[4], H. Iwasawa [4], C. H. Hong[4], K. Shimada[4], H. Namatame[4], M. Taniguchi[4], J. P. Hu[2], D. L. Feng[1]*

[1]*Department of Physics, Surface Physics Laboratory (National Key Laboratory),*
and Advanced Materials Laboratory,
Fudan University, Shanghai 200433, P. R. China

[2] *Department of Physics, Purdue University, West Lafayette, IN 47907, USA*

[3] *Department of Physics, Zhe-Jiang University,*
Hangzhou, Zhejiang 310027, P. R. China and

[4]*Hiroshima Synchrotron Radiation Center and Graduate School of Science,*
Hiroshima University, Hiroshima 739-8526, Japan.

(Dated: April 8, 2010)

Abstract

Multiple $3d$ orbitals contribute to the low energy electronic structure in the newly discovered iron-based superconductors. The specific orbital characters of the multi-bands are crucial for constructing microscopic models. We here report strong polarization dependence of the angle-resolved photoemission spectra of $BaFe_{1.85}Co_{0.15}As_2$. Our analysis identifies the orbital characters of the low lying electronic structure to be quite different from the existing calculations.

PACS numbers: 74.25.Jb,74.70.-b,79.60.-i,71.20.-b

The discovery of high temperature superconductivity in iron pnictides has ignited intensive studies on these materials [1–3]. In contrast to the cuprates, where only the $d_{x^2-y^2}$ orbital out of the five Cu $3d$-orbitals is important in the low lying electronic structure, the iron-based superconductors exhibit complex multi-band nature. Density functional theory (DFT) calculations show that its electronic structure near the Fermi energy (E_F) is mainly consisted of all the five Fe $3d$ orbitals [4, 5]. Further analysis shows that it is necessary to involve at least four bands in the Hamiltonian to model the band structure from DFT calculations [6, 7]. However, there have been inconsistencies over the orbital identities of the bands amongst theories [4–7], and a few scattered experiments [8–11]. The orbital characters are directly related to physical properties in both spin density wave (SDW) states [12] and superconducting states [13–15]. It is thus essential to experimentally identify the orbital characters of the bands near E_F, which would facilitate the construction of correct models for the iron-based superconductors.

In this paper, we report a systematic study of the orbital nature of the electronic structure of $\mathrm{BaFe_{1.85}Co_{0.15}As_2}$ near E_F by exploiting the polarization-sensitivity of the orbitals in angle-resolved photoemission spectroscopy (ARPES). We have observed strong polarization dependence for all the bands near E_F, and identify their possible orbital characters by analyzing the intensity asymmetry detected on opposite sides of Γ. The observed polarization dependence can not be understood in the current available five-band models [6, 7] and also differs from that in the SDW states of parent compounds reported recently [9, 11]. Our result gives strong constraint on the theory of iron-based superconductors and suggests that the doping may strongly influence the band structure due to strong electron-electron correlations.

$\mathrm{BaFe_{1.85}Co_{0.15}As_2}$ single crystals were synthesized by self-flux method [16] with a superconducting T_c of 25K, and no SDW or structure transitions. As a result, the low temperature electronic structure is free from the complications of the band splitting and folding [8, 17]. Data were taken with 40 eV photons at the Beamline 1 of Hiroshima synchrotron radiation center (HSRC), or with 100 eV photons at the SIS beamline of Swiss Light Source (SLS). By rotating the light polarization at SLS or the entire photoemission spectroscope around the incoming photon beam at HSRC, two different polarization geometries were achieved as shown in Fig. 1(a). The incident beam and the sample surface normal define a mirror plane. For the π (or σ) experimental geometry, the electric field direction of the incident photons

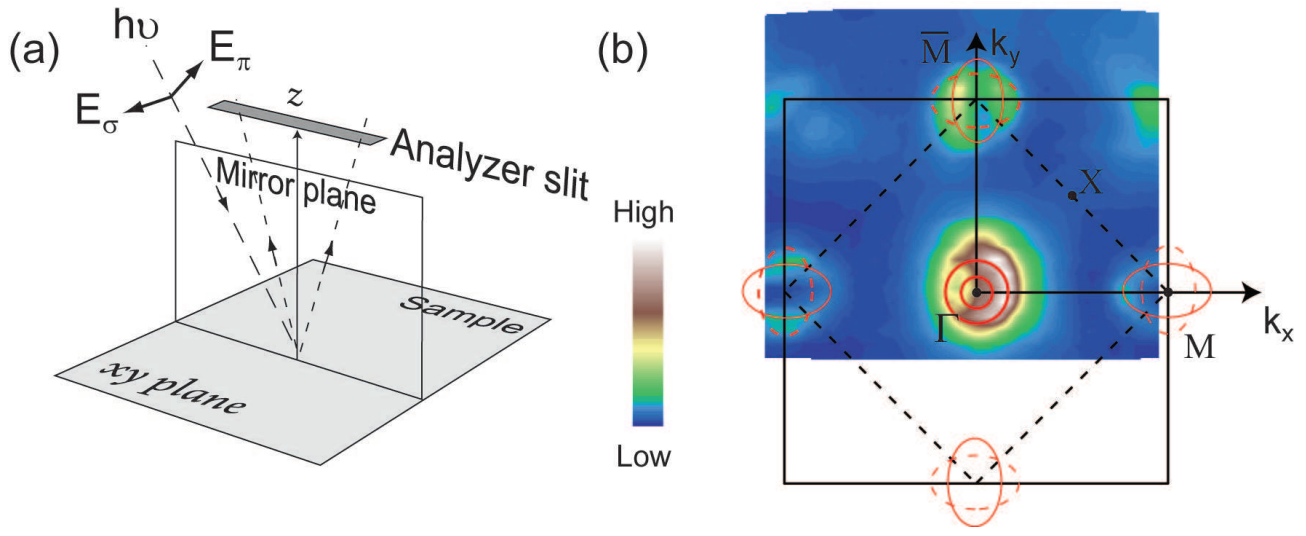

FIG. 1: (color online) (a) Experimental setup for polarization-dependent ARPES. (b) Photoemission intensity map of $\mathrm{BaFe_{1.85}Co_{0.15}As_2}$ at E_F in the Brillouin zone (dashed line). k$_x$ and k$_y$ are set with the unfolded Brillouin zone (solid line). The data were taken in the π geometry with 100 eV photons. The measured Fermi surfaces are shown in red lines, among which the Fermi pockets around M induced by zone folding are plotted in dashed lines.

is in (or out of) the mirror plane. All the data were taken with Scienta electron analyzers at 10K, the overall energy resolution is 15meV, and angular resolution is 0.3 degree. The sample was cleaved *in situ*, and measured under ultra-high-vacuum of $1 \times 10^{-10} torr$.

Photoemission intensity map at E_F for $\mathrm{BaFe_{1.85}Co_{0.15}As_2}$ is shown in Fig. 1(b). There are two hole pockets around Γ and several electron pockets around M. Because of the appearance of Arsenic ions, there are two iron ions per unit cell. The unfolded Brillouin zone for one iron ion per unit cell is shown by solid lines in Fig. 1(b). The electron pockets near M plotted in dashed lines are caused by zone folding. We assign $\Gamma - M$ as the k_x direction.

Let us first consider the electronic structure around Γ in the Γ-M direction. Photoemission data taken in σ and π geometries are compared in Fig. 2. Two sets of bands could be observed in the π geometry (assigned as α and β band respectively), while only the α band is obviously observed in the σ geometry (there are some very weak traces of β band near E_F). Note that the dispersion of the α band changes slightly in two experimental geometries [Figs. 2(c) and 2(g)], possibly due to the influence of the β band in the π geometry.

The matrix element of the photoemission process can be described by

$$|M^{\mathbf{k}}_{f,i}| \propto |\langle\phi^{\mathbf{k}}_f|\hat{\varepsilon}\cdot\mathbf{r}|\phi^{\mathbf{k}}_{\mathbf{i}}\rangle|^{\mathbf{2}}$$

, where $\hat{\varepsilon}$ is the unit vector of the electric field of the light [18]. For high kinetic-energy photoelectrons, the final-state wavefunction $\phi^{\mathbf{k}}_f$ can be approximated by a plane-wave state $e^{i\mathbf{k}\cdot\mathbf{r}}$ with $\mathbf{k}$ in the mirror plane for the analyzer slit setup in Fig. 1(a). As a result, it is even with respect to the mirror plane. For the photoemission process to be symmetry-allowed,

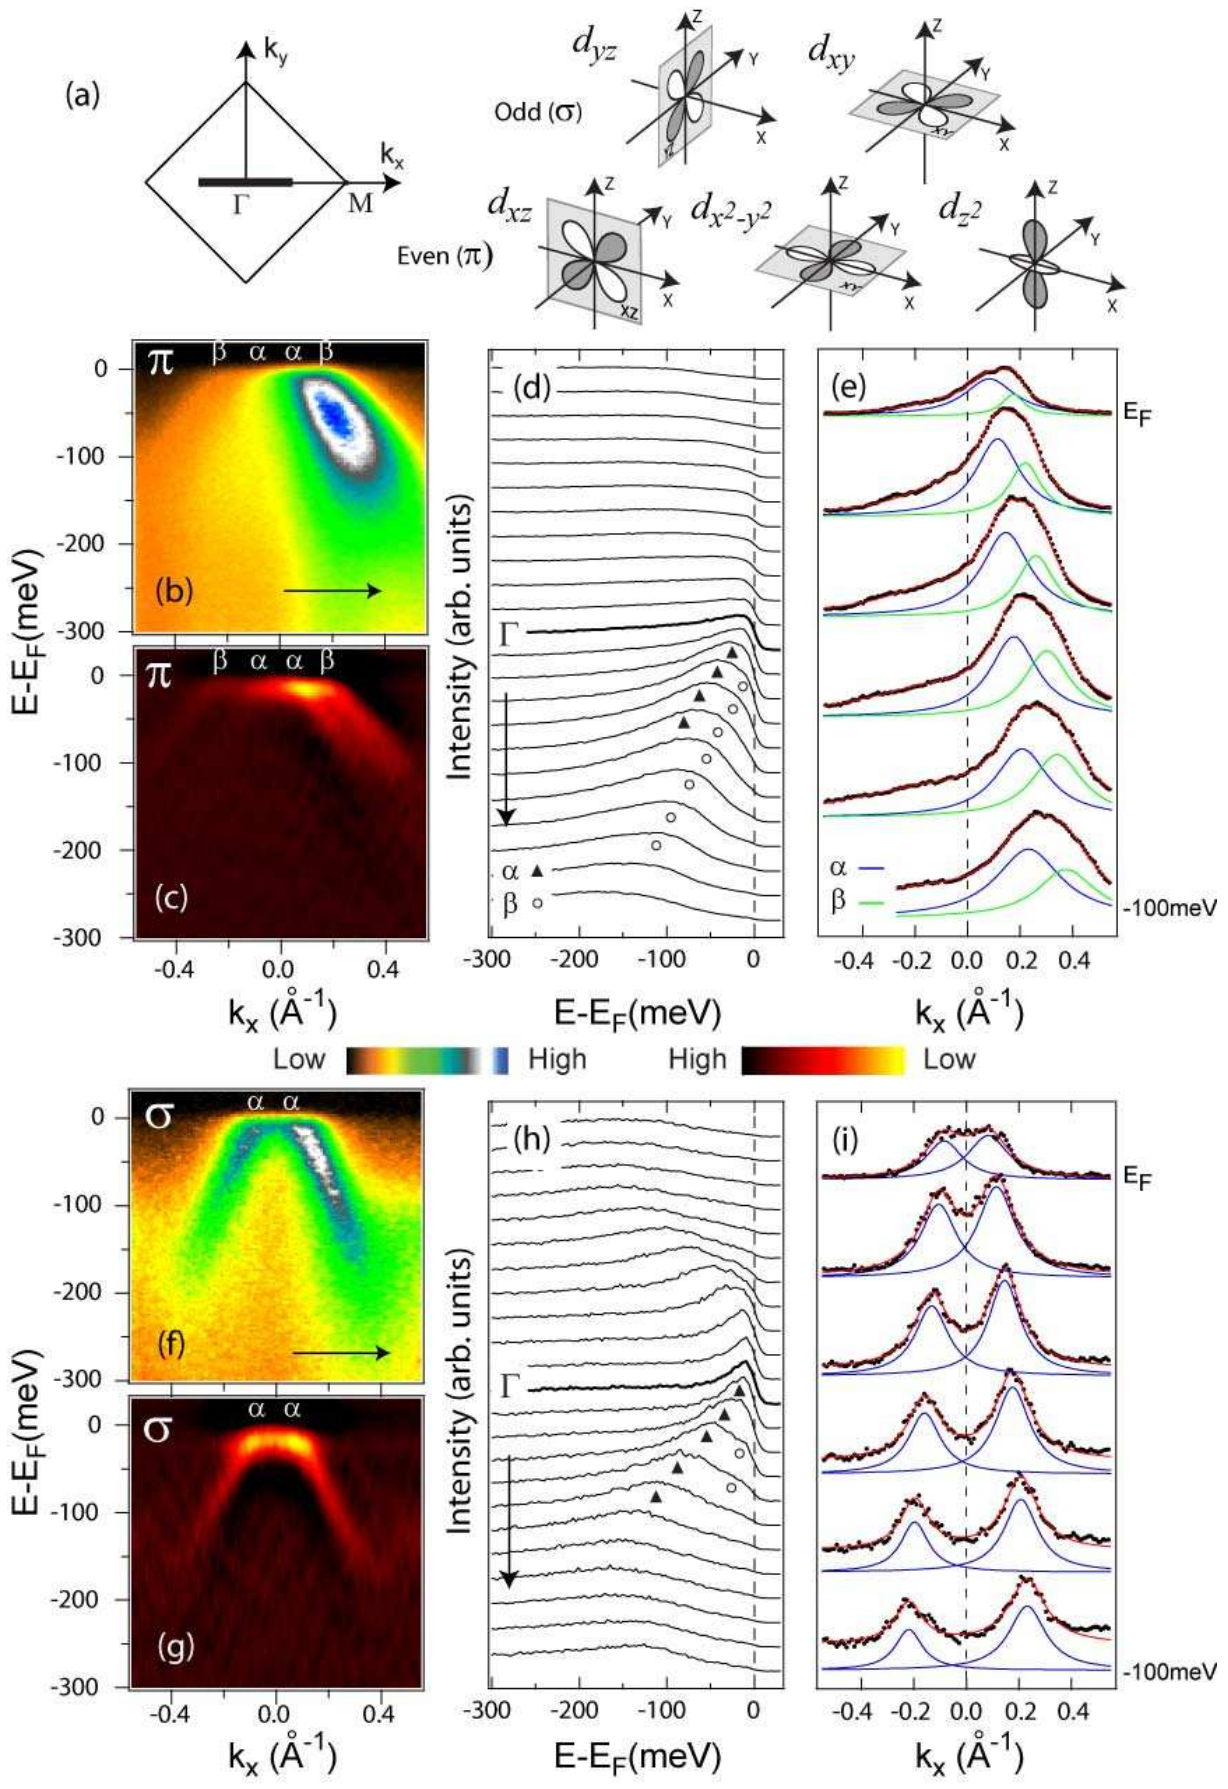

FIG. 2: (color online) The polarization dependent APRES data around Γ along the Γ-M direction. (a) The momentum cut for the presented data is marked with a thick solid line in the Brillouin zone. The symmetries of the five 3d-orbitals are illustrated. (b) Photoemission intensity taken with π geometry. (c) The second derivative with respect to energy of the data in panel b, whose minimal locus gives the band structure visually. (d) The energy distribution curves (EDC's) for the data in panel b. (e) The momentum distribution curves (MDC's) and the fitting results for the data in panel b. (f, g, h and i) are the same as in panel b, c, d and e respectively, but taken with σ geometry.

$(\hat{\varepsilon}\cdot\mathbf{r})|\phi_{\mathbf{i}}^{\mathbf{k}}\rangle$ must be even. In turn, it gives that the initial state wavefunction $\phi_i^{\mathbf{k}}$ must be even (or odd) with respect to the mirror plane in the π (or σ) experimental geometry.

With respect to the xz-plane, the d_{yz} and d_{xy} orbitals are odd, and the d_{xz}, $d_{x^2-y^2}$ and d_{z^2} orbitals are even, as illustrated in Fig. 2(a). Therefore, the β band that almost disappears in σ geometry is dominated by the d_{xz}, $d_{x^2-y^2}$ or d_{z^2} orbitals. On the other hand, the α band could be observed in both geometries. Based on the MDC's in Figs. 2(e) and 2(i), the

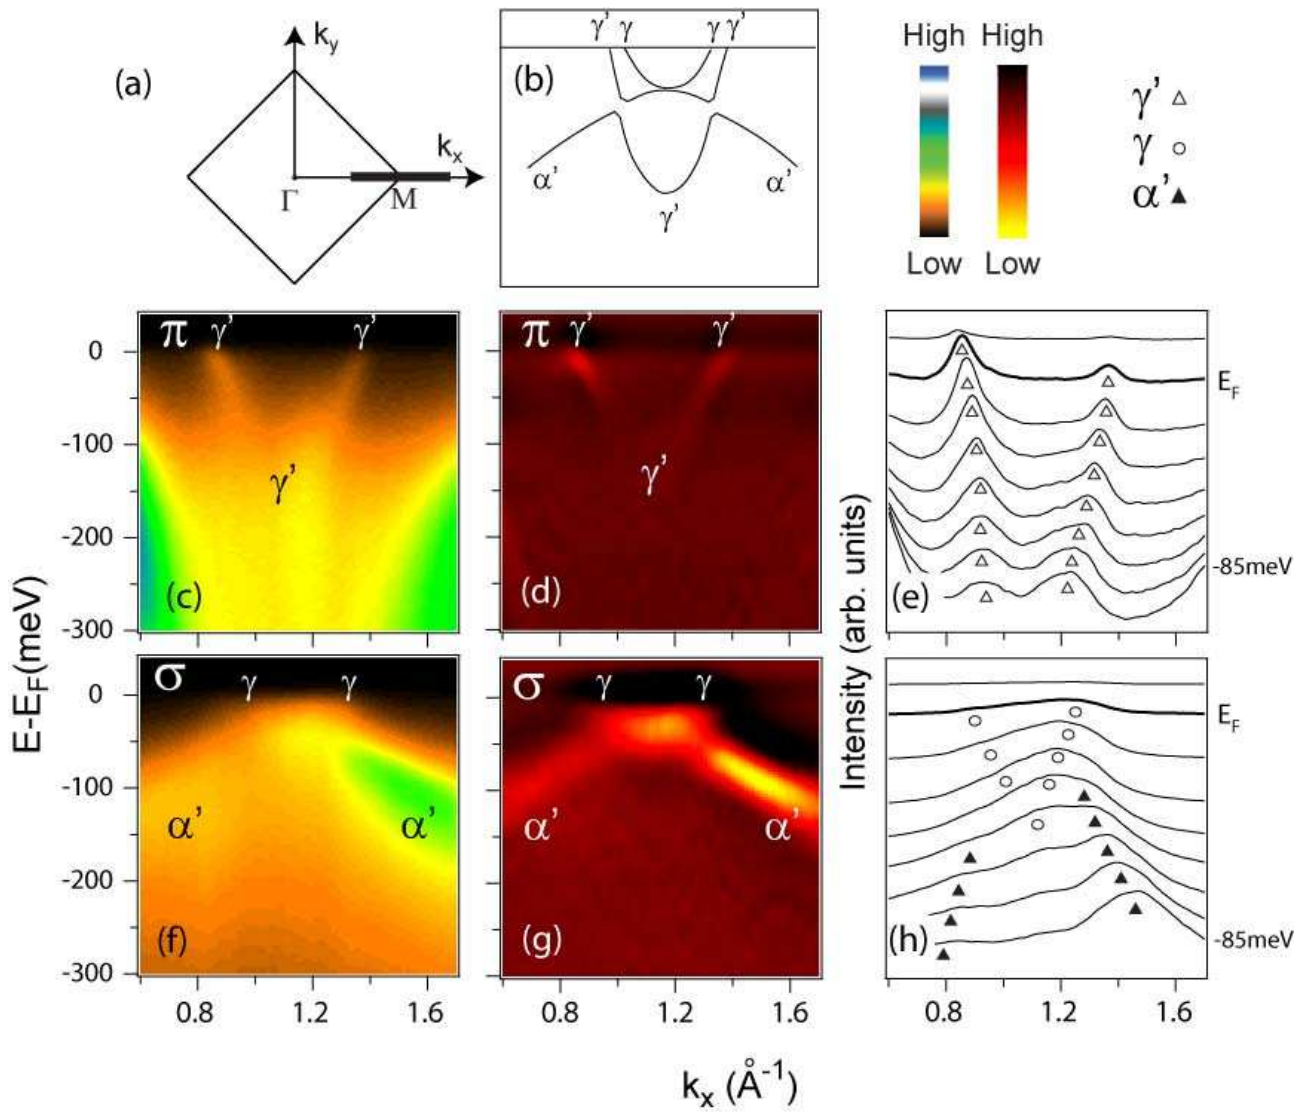

FIG. 3: (color online) The polarization dependent APRES data around M along the Γ-M direction, as marked with a thick solid line in the Brillouin zone in (a). (b) The sketch of the band structure in panel d and g. (c) Photoemission intensity and (d) its second derivative with respect to energy taken with π geometry along the cut shown in panel a. (e) The MDC's for the data in panel c. (f, g and h) are the same as in panel c, d and e, but taken with σ geometry. Data were taken with 100 eV photons.

α band has even stronger intensity than the β band in π geometry. Therefore, the α band contains both even and odd orbitals significantly.

Further along the $\Gamma - M$ cut, the states around M also show strong polarization dependence [Fig. 3]. Band calculations predicted two bands around M that cross E_F as sketched in Fig. 3(b) [4, 5, 7], which have been observed before [9, 10]. The γ' band shows up in the π geometry [Figs. 3(c-e)], while the γ and α' bands show up in the σ geometry [Figs. 3(f-h)]. We can thus conclude that near E_F, γ' is primarily consisted of d_{xz}, $d_{x^2-y^2}$, or d_{z^2} orbitals, while γ and α' are made of d_{xy} or d_{yz} orbitals [Fig. 3(g)]. It has been suggested that both γ and γ' bands are of even symmetry in the SDW state of $SrFe_2As_2$ [9]. However, note that our data are consistent with the normal state data of $BaFe_2As_2$ in Ref.[10], thus, the discrepancy suggests that the SDW or doping might influence the electronic structure significantly. We leave this to further investigations in the future.

The observed orbital characters are hard to be understood within the current band calculation results [6, 7]. Considering the five-band models constructed by fitting the LDA

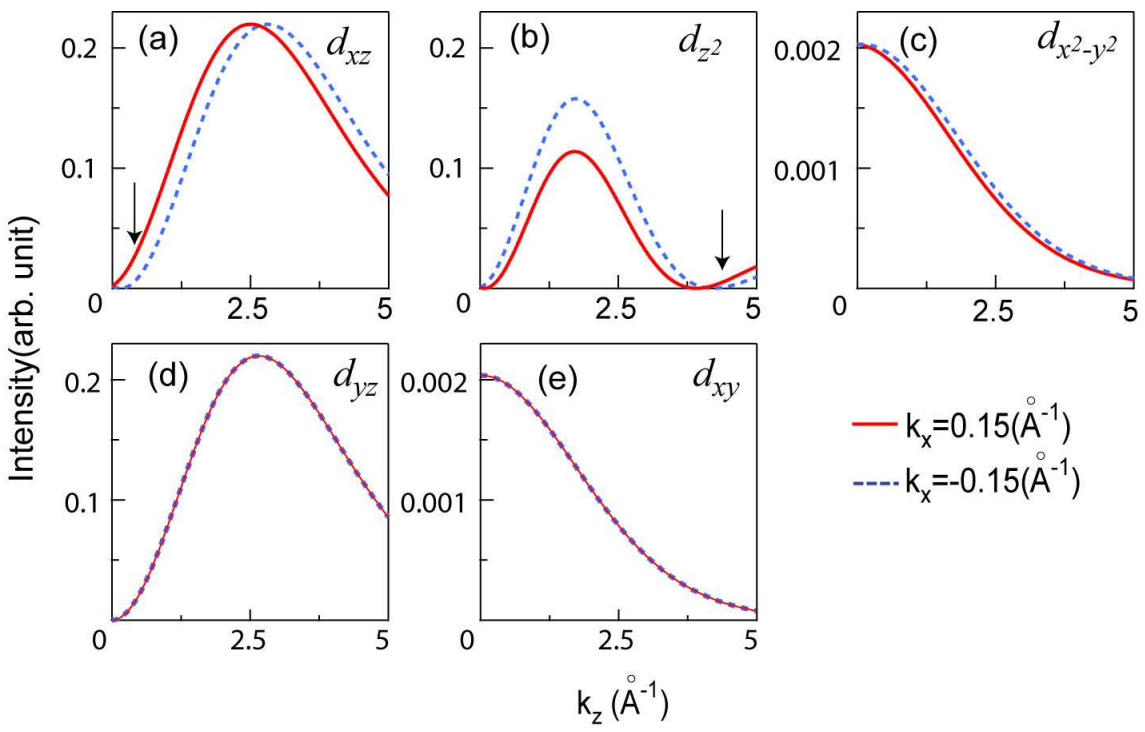

FIG. 4: (a), (b) and (c) are the simulation of the matrix element of d_{xz}, d_{z^2} and $d_{x^2-y^2}$ in π geometry respectively. (d) and (e) are the simulation of the matrix element of d_{yz} and d_{xy} in σ geometry respectively. The arrows in panels a and b indicate the momentum position where the experimental intensity asymmetry can be achieved.

results in the unfolded Brillouin zone, the two hole pockets around Γ mainly contain d_{xz} and d_{yz} orbitals. More explicitly, along $\Gamma - M$, states at the inner (α) and outer (β) pockets are mainly attributed to d_{xz} and d_{yz} orbitals respectively [6, 7]. Since the α band contains both odd and even components (named as α_π and α_σ respectively hereafter), the d_{xz} with even symmetry alone cannot account for the observation. Moreover, the β band is largely suppressed in σ geometry, and thus it must be mostly even, while theory predicted it to be odd (d_{yz}). Similarly around M, the calculations suggest that the large and small electron pockets along $\Gamma - M$ are made of the d_{xy} and d_{yz} orbitals respectively, both of which are odd. But in experiments, the large (γ') and the small (γ) pockets show even and odd symmetry respectively.

There is another important constraint put by the experiment. Namely in the π geometry, the intensities of the same band on opposite sides of Γ show a strong asymmetry of R=$I(k_{x+})/I(k_{x-}) \sim 5$ in Figs. 2(d) or 2(e). To understand this, Fig. 4 shows the calculated photoemission matrix elements in the π geometry for the d_{xz} , d_{z^2} and $d_{x^2-y^2}$ contributions to the photoemission matrix element at $k_x = \pm 0.15\mathring{A}^{-1}$, and k_z in the range of 0 to $5\mathring{A}^{-1}$. We have neglected the possible complication from the k_z dispersion, since it is not so prominent in the non-SDW state [11, 19]. To fit the experimental intensity asymmetry, the final state k_z is about $0.4\mathring{A}^{-1}$ for the d_{xz} case [Fig. 4(a)]. The photoemission matrix element of d_{z^2} is comparable with that of d_{xz}, but has the opposite asymmetry at low k_z. On the other hand,

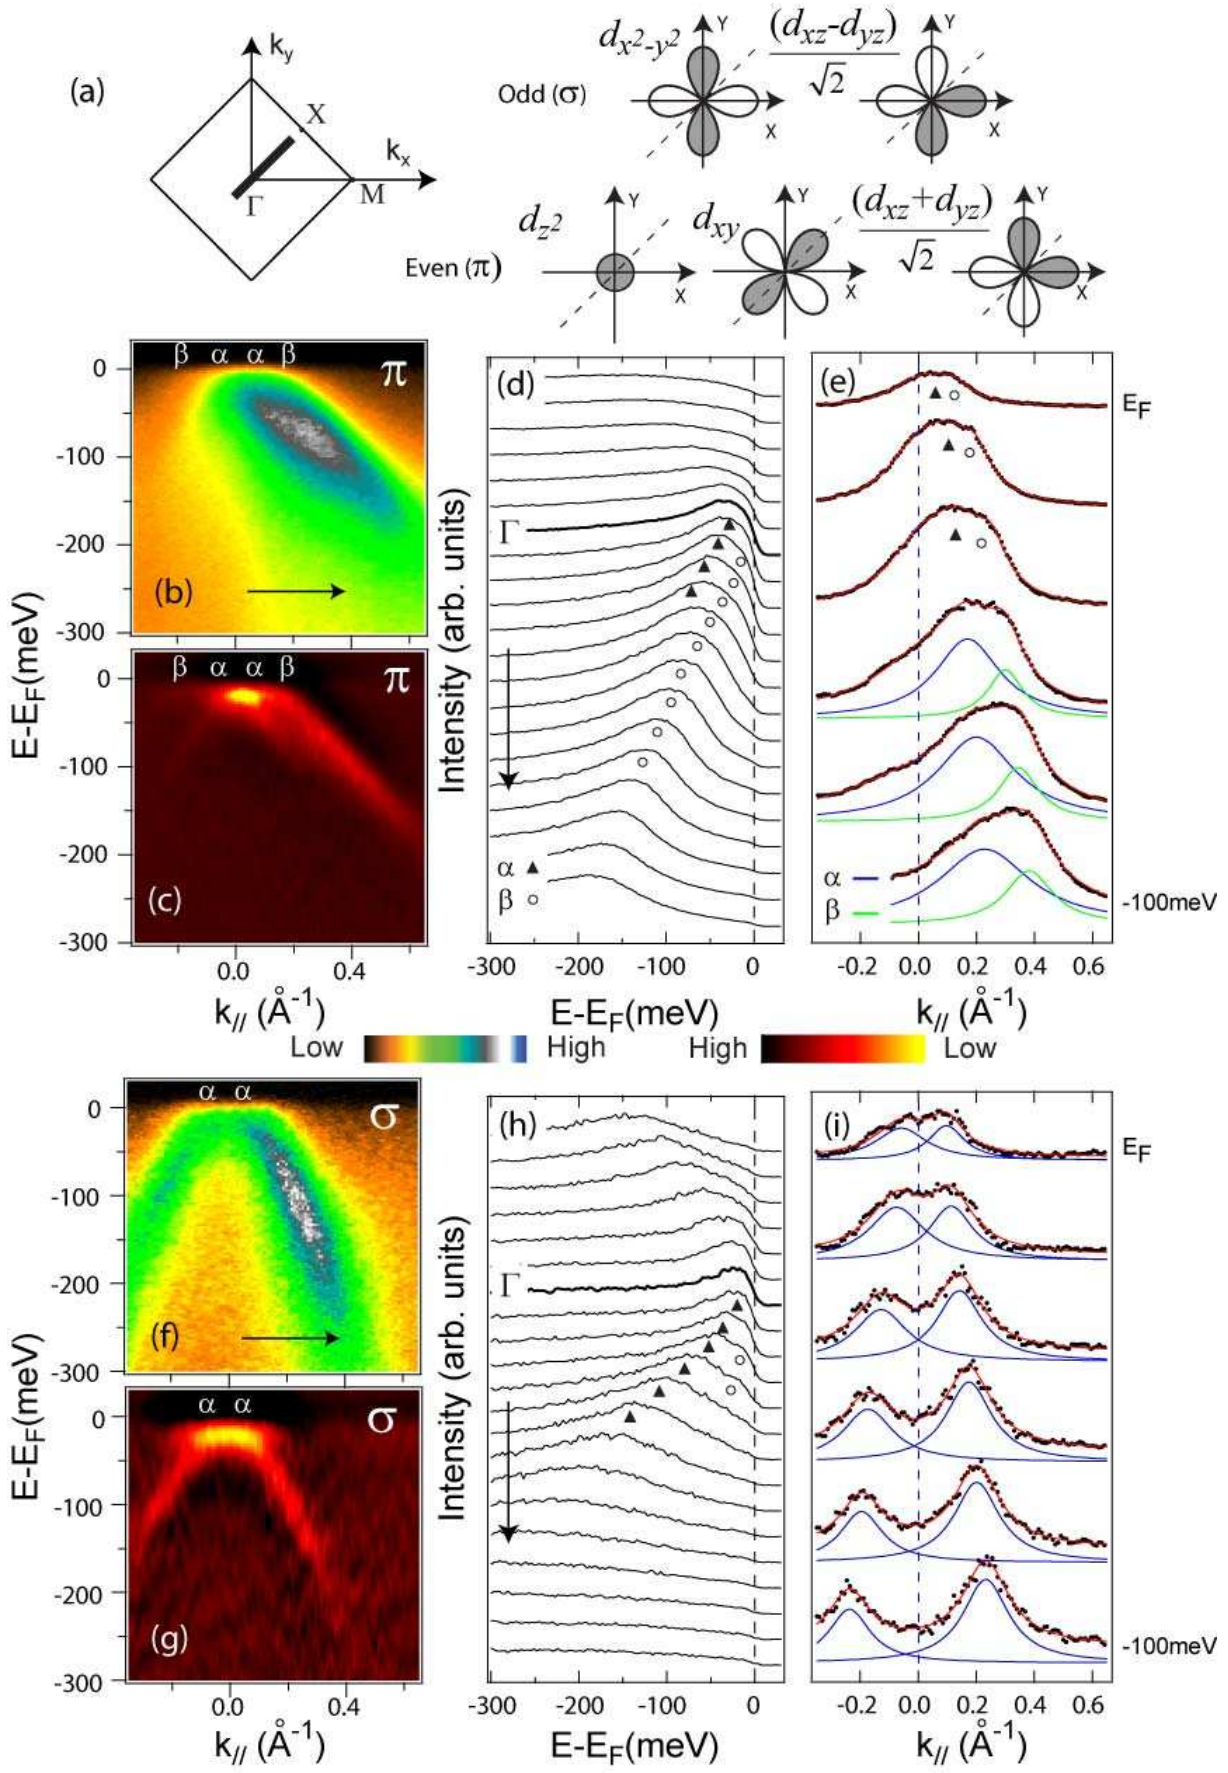

FIG. 5: (color online) APRES data around Γ along the Γ-X direction. (a) The momentum cut for the presented data is marked with a thick solid line in the Brillouin zone. The symmetries of the five $3d$-orbitals are illustrated. (b) Photoemission intensity and (c) its second derivative with respect to energy taken with π geometry. (d) the EDC's for the data in panel b. (e) the MDC's and the fitting results for the data in panel b. (f, g, h and i) are the same as in panel b, c, d and e respectively, but taken with σ geometry.

the matrix element of d_{z^2} can fit the experimental asymmetry at $k_z = 4.4\mathring{A}^{-1}$ [Fig. 4(b)], where d_{xz} contributes almost equally strong intensities to both sides. Thus, the asymmetry of our spectrum demands that either single d_{z^2} or d_{xz} orbital should dominate the bands near Γ. While our current experimental result can not further pin down the exact orbital, considering the fast in-plane dispersion in the $\Gamma - M$ direction and the known band structure calculations [4, 5], we conclude that there is little contribution of d_{z^2} to the Fermi surface near Γ. The photoemission cross-section of $d_{x^2-y^2}$ is two order of magnitude smaller than the other two near Γ [Fig. 4(c)]. Therefore, although there may be strong mixing of $d_{x^2-y^2}$

orbitals, it contributes negligibly to the measured photoemission intensity. This behavior of $d_{x^2-y^2}$ has been observed in cuprates, where very little spectral weight can be observed near Γ [20]. Because the intensity of the α_π component is even somewhat stronger than that of the β band [Fig. 2(e)], the β band should not be composed of single d_{xz} or $d_{x^2-y^2}$ orbitals, but rather strong hybridizations of both d_{xz} and $d_{x^2-y^2}$ orbitals, and the α_π component contains more d_{xz} state than the β band. On the other hand, our calculation shows that for low k_x, the d_{xy} orbital contributes little to photoemission intensity compared with the d_{yz} orbital [Figs.4(d-e)], therefore, the α_σ component contains sizable d_{yz} plus possible d_{xy} orbital (Table. I).

To further determine the orbital characters for the bands around Γ, we rotate the mirror plane by 45° with respect to z-axis, to the Γ-X direction. Photoemission intensity along the Γ-X direction in two geometries are shown in Fig. 5. The polarization dependence of the α and β bands resembles that in Fig. 2. The d_{xy} and d_{z^2} orbitals are even, and the $d_{x^2-y^2}$ orbital is odd in this setup. Although d_{xz} and d_{yz} orbitals are not symmetric as shown in Fig. 5(a), their hybridized orbitals, $\frac{d_{xz}+d_{yz}}{\sqrt{2}}$ and $\frac{d_{xz}-d_{yz}}{\sqrt{2}}$, have even and odd symmetry respectively. Therefore, along the Γ-X direction, the outer pocket should have d_{xy}, d_{z^2} or $\frac{d_{xz}+d_{yz}}{\sqrt{2}}$ orbital characters. The inner pocket should mainly be the mixture of both even and odd orbitals. Similar polarization dependence behaviors are observed when the mirror plane is rotated by another 45° to the yz plane, as expected from the 4-fold symmetry of the system. These indicate that the d_{xz} portion in α_π and β along the $\Gamma - M$ direction is evolving to $\frac{d_{xz}+d_{yz}}{\sqrt{2}}$ in the $\Gamma - X$ direction, and to d_{yz} in the $\Gamma - \overline{M}$ direction; while the sizable d_{yz} portion in α_σ evolves to $\frac{d_{xz}-d_{yz}}{\sqrt{2}}$ and to d_{xz} respectively.

We summarize our experimental orbital assignments of the bands in Table-I. A few remarks are listed as follows: (1) Strong polarization dependence has been reported recently by several ARPES groups [9–11]. These experiments were done on the parent compounds of iron-based superconductors. The analysis of orbital characters from these experiments was not straightforward due to the presence of lattice distortion and magnetic ordering. Our results show significant differences compared to those in the SDW states [9, 11] as pointed out above. (2) Our results suggest that there are distinct orbital characters for the most bands near Fermi surface. This property is very important for constructing microscopic models and investigating physical properties such as disorder effects. (3) Our comprehensive analysis does not fully rule out the possible major presence of d_{z^2} at Fermi surfaces, which is possible

TABLE I: The main orbital characters of the bands near E_F along the $\Gamma - M$ direction.

	α_π	α_σ	β	γ	$\gamma^{'}$	$\alpha^{'}$
d_{xz}	sizable		some		possible	
$d_{x^2-y^2}$	possible		strong		possible	
d_{z^2}					possible	
d_{yz}		sizable	minute	possible		possible
d_{xy}		possible	minute	possible		possible

when strong electron-electron correlation is included [21]. (4) The current five-band models cannot explain our experiments, which is not entirely unexpected. For example, the Fermi sphere in the $\Gamma - Z$ direction, which was predicted by band calculations and attributed to d_{z^2} in $BaFe_2As_2$ compounds, has never been observed so far. The discrepancy between the theoretical band structures and our experimental results suggests that electron-electron correlation may play an important role.

To summarize, we have carried out a systematic investigation of orbital characters in $BaCo_{0.15}Fe_{1.85}As_2$ and have analyzed all the possible orbital characters of each bands based on strong polarization-dependent photoemission response of the low-lying electronic structure. We find that most bands near Fermi surface have distinct orbital characters. Our explicit conclusions cannot be understood in the current band calculations, and put strong constraints on the theory of iron-based superconductors.

This work was supported by the NSFC, MOE, MOST (National Basic Research Program No.2006CB921300), STCSM of China, the NSF of US under grant No. PHY-0603759, and HSRC under proposal 08-A-28. We gratefully acknowledge the experimental support by Dr. X. Y. Cui and Prof. L. Patthey at SLS.

---

* Electronic address: dlfeng@fudan.edu.cn

[1] Y. Kamihara *et al.*, J. Am. Chem. Soc., **130**, 3296 (2008).

[2] X. H. Chen *et al.*, Nature, **453**, 761 (2008).

[3] Z. A. Ren *et al.*, Chin. Phys. Lett. **25**, 2215 (2008).

[4] D. J. Singh and M. H. Du, Phys. Rev. Lett. **100**, 237003 (2008).

[5] F. Ma, Z. Y. Lu and T. Xiang, arXiv:0806.3526[cond-mat.supr-con].

[6] Kazuhiko. Kuroki *et al.*, Phys. Rev. Lett. **101**, 087004 (2009).

[7] S. Graser *et al.*, New J. Phys. **11**, 025016 (2009)

[8] L. X. Yang *et al.*, Phys. Rev. Lett. **102**, 107002 (2009).

[9] D. Hsieh *et al.*, arXiv:0812.2289[cond-mat.supr-con].

[10] M. Yi *et al.*,arXiv:0902.2628[cond-mat.supr-con].

[11] T. Shimojima *et al.*, arXiv:0904.1632[cond-mat.supr-con].

[12] Y. Ran *et al.*, Phys. Rev. B **79**, 014505 (2009).

[13] K. Seo *et al.*, Phys. Rev. Lett. **101**, 206404 (2008).

[14] Y. Y. Zhang *et al.*, arXiv:0903.1694[cond-mat.supr-con].

[15] A.V. Chubukov, *et al.*, arXiv:0903.5547[cond-mat.supr-con].

[16] L. J. Li *et al.*, New J. Phys. **11**, 025008 (2009)

[17] Y. Zhang *et al.*, Phys. Rev. Lett. **102**, 127003 (2009).

[18] A. Damascelli *et al.*, Rev. Mod. Phys. **75**, 473 (2003).

[19] C. Liu *et al.*, arXiv:0903.4388[cond-mat.supr-con].

[20] B. P. Xie *et al.*, Phys. Rev. Lett. 98, 147001 (2007).

[21] G. T. Wang *et al.*, arXiv:0903.1385[cond-mat.supr-con].